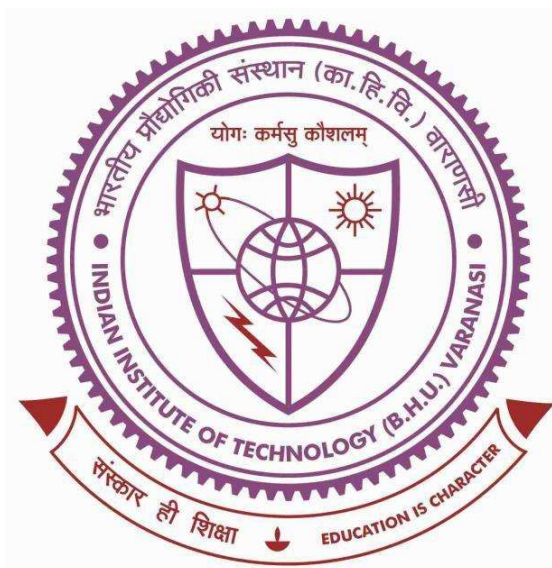


***Ratcheting Fatigue Behaviour of
Modified 9Cr-1Mo Steel and Superalloy Inconel 617***



**Thesis submitted in partial fulfilment for the
Award of Degree**

DOCTOR OF PHILOSOPHY

By

Prerna Mishra

**DEPARTMENT OF METALLURGICAL ENGINEERING
INDIAN INSTITUTE OF TECHNOLOGY
(BANARAS HINDU UNIVERSITY) VARANASI-221005**

16141005

2022

CERTIFICATE

It is certified that the work contained in the thesis titled "*Ratcheting Fatigue Behaviour of Modified 9Cr-1Mo Steel and Superalloy Inconel 617*" by "*Prerna Mishra*" has been carried out under my supervision and that this work is not submitted anywhere else for any degree.

It is further certified that the student has satisfactorily fulfilled all the requirements of Comprehensive examination, Candidacy and SOTA for the award of the PhD degree.

NC Santhi Srinivas
Prof. N.C. Santhi Srinivas

(Supervisor)

Department of Metallurgical Engineering
प्राचार्य/Professor

धातुक्रीय अभियांत्रिकी विभाग
Indian Institute of Technology
Department of Metallurgical Engg.
भारतीय प्रौद्योगिकी संस्थान (काशी हिन्दू विश्वविद्यालय)
(Banaras Hindu University)
Varanasi-221005/Varanasi-221005

Varanasi-221005

DECLARATION BY THE CANDIDATE

I, "Prerna Mishra", certify that the work embodied in this thesis is my own bonafide work carried out by me under the supervision of "Prof. N.C. Santhi Srinivas" from "July 2016" to "July 2022", at the "Department of Metallurgical Engineering", Indian Institute of Technology (BHU), Varanasi. The matter embodied in this thesis has not been submitted for the award of any other degree/diploma. I declare that I have faithfully acknowledged and given credits to the research workers wherever their works have been cited in my work in this thesis. I further declare that I have not wilfully copied any other's work, paragraphs, text, data, results, etc., reported in journals, books, magazines, reports dissertations, thesis, etc., or available at websites and have not included them in this thesis and have not cited as my own work.

Date: 02/01/2023

Prerna Mishra

Prerna Mishra

CERTIFICATE BY THE SUPERVISOR

This is to certify that the above statement made by the candidate is correct to the best of our knowledge.

N.C. Santhi Srinivas
Prof. N.C. Santhi Srinivas 2-1-2023
(Supervisor)

Department of Metallurgical Engineering
Indian Institute of Technology (Banaras Hindu University)
Indian Institute of Technology (Banaras Hindu University)
वाराणसी-221005/Varanasi-221005

Dr. Sunil Mohan
(Professor and Head)

Department of Metallurgical Engineering
Indian Institute of Technology (Banaras Hindu University)
Department of Metallurgical Engineering
भारतीय प्रौद्योगिकी संस्थान (काशी हिन्दू विश्वविद्यालय)
Indian Institute of Technology (Banaras Hindu University)
वाराणसी-221005/Varanasi-221005

COPYRIGHT TRANSFER CERTIFICATE

Title of the Thesis: *"Ratcheting Fatigue Behaviour of Modified 9Cr-1Mo Steel and Superalloy Inconel 617"*

Name of the Student: *Prerna Mishra*

COPYRIGHT TRANSFER

The undersigned hereby assigns to the Indian Institute of Technology (Banaras Hindu University) Varanasi all rights under copyright that may exist in and for the above thesis submitted for the award of the *"Ph.D. Degree"*.

Date: *02/01/2023*


Prerna Mishra

Note: However, the author may reproduce or authorize others to reproduce material extracted verbatim from the thesis or derivative of the thesis for author's personal use provided that the source and the Institute's copyright notice are indicated.

Dedicated to
My Family

ACKNOWLEDGMENTS

I begin my thanks giving and acknowledgements by paying my obeisance to Lord Shree Kashi Vishwanath, Mata Annapurne and my Guru.

I hereby to express my deep sense of appreciation and everlasting indebtedness to my supervisor, **Prof. N.C. Santhi Srinivas**, Department of Metallurgical Engineering, IIT (BHU), for her meticulous guidance and whole hearted co-operation in carrying out this work. Her inspiring comments and suggestions motivated me to continue my research work. From her remarkable support and advice during my Ph.D, I gained a lot of experience and knowledge. It was really a precious and unique experience to work under her able guidance.

I would like to express my deepest sense of gratitude to Prof. Vakil Singh and Prof. G.V.S Sastry for continuous help and inspiration and also in carrying out in-depth analysis of the outcomes of the research work and inspiration throughout my research. This thesis would not have been completed without their involvement and efforts. I consider myself extremely fortunate to have had supervisors that genuinely cared about my work and responded to my queries in a timely manner.

I am highly thankful to Prof. Sunil Mohan Head of the Department and former Heads Prof. N. K. Mukhopadhyay and Prof. R.K. Mandal for providing all the research facilities to successfully complete my research in the Department. Beside my Supervisor, I would like to thank other members of RPEC: Dr. K. Chattopadhyay, Department of Metallurgical Engineering and Dr. S.K. Panda, Department of Mechanical Engineering, for their insightful comments and encouragement. My sincere thanks also go to Dr. R. Manna, Dr. G.S. Mahobia, Dr. A.K. Mondal and all other faculty members of the Department of Metallurgical Engineering, IIT (BHU), for their co-operation and inspiration.

I am obliged to all my seniors Dr. Preeti Verma, Dr. Vaibhav Pandey, Dr. Rupendra Singh Rajpurohit, Dr. Vikas Shivam, Dr. Ch.V. Rao, and Dr. Asnit Gangwar for their needful help. I am also thankful to my colleagues, Pramod, Avnish, Sandeep, Jaydeep, Vasu, Aman, Urvashi, Debabrata, Roopchand for making joyful and memorable life and being with my moments of happiness and troubles at IIT (BHU), Varanasi. I am also thankful to all my junior students M.Tech and PhD of our group from 2016 to 2022 for their support during my research work.

I am also thankful to all the Lab and workshop staff specially Mr. Kamlesh, Mr. Susheel, Mr. Minz, Mr. Anjani, Mr. Balwant, Mr. Mangal, Mr. Deepak, Mr. Ajay and Mr. Rajnarayan for helping in preparation of fatigue and tensile samples. I would also like to thank Mr. Lalit Kumar Singh, Mr. Ashok Kumar for helping in scanning and transmission electron microscopy. I would also like to extend my heartiest thanks to Prof. Rajiv Prakash (Prof. In-charge, CIFIC) and Mr. Girish Sahu, Mr. Vinay and for their needful help in SEM, TEM and other research facilities. My thanks to Mr. Patel, Mr. Rana, and all the other office and lab staff of the department.

I would also like to acknowledge the Ministry of Human Resource and Development, Government of India for providing teaching assistantship during the entire period of my Ph.D. Last, but not the least, I would like to express my deepest gratitude to my parents Mr. R.K. Mishra and Mrs. Vimla Mishra and my spouse Dr. Vivek Gupta and my son Raghav for their unconditional love, support and encouragement to pursue my interest.

I also wish to thank all my friends and the persons whose names have not been mentioned on this piece of paper for extending their co-operation directly or indirectly.



Prerna Mishra

TABLE OF CONTENTS

	Page No
List of figures	i-xii
List of tables	xiii-xvi
List of symbols	xvii-xviii
Preface	xix-xxiv
CHAPTER 1 INTRODUCTION	1-41
1.1	Cyclic loading 1
1.2	Ratcheting 2
1.3	Ratcheting strain 4
1.4	Alloys investigated 7
1.4.1	Modified 9Cr-1Mo steel 7
1.4.1.(i)	Development of Cr-Mo steels 7
1.4.1.(ii)	Physical metallurgy of Cr-Mo steels 9
1.4.1.(iii)	Properties of modified 9Cr-1Mo steel 14
1.4.2	Superalloy Inconel 617 14
1.4.2.(i)	Nickel based superalloys 16
1.4.2.(ii)	Nickel-based superalloy Inconel 617 19
1.4.2.(iii)	Physical Metallurgy of Inconel 617 alloy 21
1.4.2.(iv)	Properties of Inconel 617 alloy 23
1.5	Applications 23
1.6	Ratcheting behaviour of advanced structural materials 24
1.6.1	Ratcheting at specimen level 26
1.6.1.(i)	Effect of applied stress levels (mean stress and stress amplitude) 26
1.6.1.(ii)	Influence of stress rate 28
1.6.1.(iii)	Influence of mean stress direction 30
1.6.1.(iv)	Effect of temperature 31
1.6.1.(v)	Effect of crystal structure 32
1.6.2	Modes of experimentation 33
1.6.3	Effect of ratcheting on mechanical behaviour 35
1.6.4	Microstructural characterization 37
1.6.5	Ratcheting at component level 38
1.7	Motivation for this work 40
1.8	Objectives of the present investigation 41
CHAPTER 2 MATERIALS AND METHODS	42-51
2.1	Introduction 42
2.2	Materials 42
2.3	Mechanical Testing 43
2.3.1	Tensile Testing 43

2.3.2	Ratcheting Fatigue Testing	44
2.4	Microstructural Characterization	48
2.4.1	Optical Microscopy	48
2.4.2	Scanning Electron Microscopy	49
2.4.3	Transmission Electron Microscopy	50
2.5	Summary	51
CHAPTER 3	RATCHETING FATIGUE BEHAVIOUR OF MODIFIED 9Cr-1Mo STEEL AT ROOM TEMPERATURE	52-85
3.1	Introduction	52
3.2	Microstructural characterization of modified 9Cr-1Mo steel	52
3.3	Tensile properties of modified 9Cr-1Mo steel	54
3.4	Uniaxial ratcheting fatigue behaviour of modified 9Cr-1Mo steel	55
3.4.1	Influence of mean stress on fatigue behaviour of modified 9Cr-1Mo steel under asymmetric cyclic loading	56
3.4.2	Influence of stress amplitude on fatigue behaviour of modified 9Cr-1Mo steel under asymmetric cyclic loading	58
3.4.3	Influence of stress rate on fatigue behaviour of modified 9Cr-1Mo steel under asymmetric cyclic loading	59
3.5	Cyclic stress-strain behaviour of modified 9Cr-1Mo steel	60
3.5.1	Impact of mean stress on stress-strain behaviour of modified 9Cr-1Mo steel under asymmetric cyclic stressing	60
3.5.2	Impact of stress amplitude on stress-strain behaviour of modified 9Cr-1Mo steel under asymmetric cyclic stressing	65
3.5.3	Impact of stress rate on stress-strain behaviour of modified 9Cr-1Mo steel under asymmetric cyclic stressing	67
3.6	Influence of asymmetric stress cycling on fracture behaviour of modified 9Cr-1Mo steel	69
3.7	Deformation behaviour of modified 9Cr-1Mo steel	73
3.8	Discussion	75
3.9	Summary	83

CHAPTER 4	RATCHETING FATIGUE BEHAVIOUR OF INCONEL 617 ALLOY AT ROOM TEMPERATURE	86-118
4.1	Introduction	86
4.2	Microstructural characterization of Inconel 617 alloy	87
4.3	Tensile properties of Inconel 617 alloy	88
4.4	Uniaxial ratcheting fatigue behaviour of Inconel 617 alloy	89
4.4.1	Effect of the stress amplitude on cyclic response of Inconel 617 alloy under asymmetric cyclic loading	90
4.4.1.(a)	Fatigue tests performed with the maximum stress near the yield strength	90
4.4.1.(b)	Fatigue tests at stress amplitude of 450 to 550 MPa with maximum stress of 650 to 750 MPa, in the intermediate region between the YS and UTS	92
4.4.1.(c)	Fatigue test with maximum stress near ultimate tensile strength	93
4.4.2	Effect of mean stress on cyclic response of Inconel 617 alloy under asymmetric cyclic loading	94
4.4.3	Effect of stress rate on cyclic response of Inconel 617 alloy under asymmetric cyclic loading	96
4.5	Cyclic stress-strain behaviour of Inconel 617 alloy	97
4.5.1	Impact of stress amplitude on stress-strain behaviour of Inconel 617 alloy under asymmetric cyclic stressing	98
4.5.2	Impact of mean stress on stress-strain behaviour of Inconel 617 alloy under asymmetric cyclic stressing	100
4.5.3	Impact of stress rate on stress-strain behaviour of Inconel 617 alloy under asymmetric cyclic stressing	102
4.6	Fracture behaviour of Inconel 617 alloy	104
4.7	Deformation behaviour of Inconel 617 alloy	106
4.8	Comparison of uniaxial ratcheting behaviour of the alloys at room temperature	106
4.9	Discussion	108
4.9.1	Ratcheting fatigue behaviour of Inconel 617 alloy	108
4.9.2	Comparison of uniaxial ratcheting behaviour of the alloys at room temperature	115
4.10	Summary	117
CHAPTER 5	RATCHETING FATIGUE BEHAVIOUR OF THE ALLOYS AT ELEVATED TEMPERATURES	119-144
5.1	Introduction	119
5.2	Ratcheting fatigue behaviour of modified 9Cr-1Mo steel at 600°C	120

5.2.1	Tensile properties of modified 9Cr-1Mo steel at 600°C	120
5.2.2	Uniaxial ratcheting fatigue behaviour of modified 9Cr-1Mo steel at 600°C under the effect of mean stress	120
5.2.3	Fracture behaviour of modified 9Cr-1Mo steel at 600°C	122
5.2.4	Comparison of uniaxial ratcheting behaviour of modified 9Cr-1Mo steel at 600°C and RT	123
5.3	Ratcheting fatigue behaviour of Inconel 617 alloy at 800°C	124
5.3.1	Tensile properties of Inconel 617 alloy at 800°C	124
5.3.2	Uniaxial ratcheting fatigue behaviour of Inconel 617 alloy at 800°C under the effect of mean stress	125
5.3.3	Fracture behaviour of Inconel 617 alloy at 800°C	126
5.3.4	Comparison of uniaxial ratcheting behaviour of Inconel 617 alloy at 800°C and RT.	127
5.4	Comparison of both the alloys at homologous temperature	128
5.4.1	Homologous temperature and its calculation	128
5.4.2	Tensile properties of both the alloys at 0.42 T_m	129
5.4.3	Uniaxial ratcheting behaviour of the alloys at 0.42 T_m	130
5.4.4	Fracture behaviour of the alloys at 0.42 T_m	134
5.5	Discussion	136
5.5.1	Comparison of ratcheting fatigue behaviour of the alloys at RT and their respective service temperatures	136
5.5.2	Comparison of ratcheting fatigue behaviour of the alloys at homologous temperature	139
5.6	Summary	143
CHAPTER 6	EFFECT OF PRE-RATCHETING ON TENSILE PROPERTIES OF ALLOYS AT ROOM TEMPERATURE	145-174
6.1	Introduction	145
6.2	Effect of pre-ratcheting on tensile behaviour of the modified 9Cr-1Mo steel, at RT	145
6.2.1	Tensile properties of the modified 9Cr-1Mo steel in normalized and tempered condition	146
6.2.2	Uniaxial ratcheting behaviour of modified 9Cr-1Mo steel	146
6.2.3	Tensile behaviour of the pre-ratcheted modified 9Cr-1Mo steel	149
6.2.3.(a)	Tensile properties of the modified 9Cr-1Mo steel pre-ratcheted at various mean stresses	149
6.2.3.(b)	Tensile properties of the modified 9Cr-1Mo steel	149

	pre-ratcheted at various stress amplitudes	
6.2.3.(c)	Tensile properties of the modified 9Cr-1Mo steel pre-ratcheted at various stress rates	150
6.2.4	Fracture Behaviour of modified 9Cr-1Mo steel	151
6.3	Effect of pre-ratcheting on tensile behaviour of Inconel 617 alloy at RT	153
6.3.1	Tensile properties of the Inconel 617 alloy in solution treated condition	154
6.3.2	Uniaxial ratcheting behaviour of Inconel 617 alloy	154
6.3.3	Tensile behaviour of the Inconel 617 alloy pre-ratcheted with different parameters	157
6.3.3.(a)	Tensile properties of the Inconel 617 alloy pre-ratcheted at various mean stresses	157
6.3.3.(b)	Tensile properties of the Inconel 617 alloy pre-ratcheted at various stress amplitudes	159
6.3.3.(c)	Tensile properties of the Inconel 617 alloy pre-ratcheted at various stress rates	161
6.3.4	Fracture Behaviour of Inconel 617 alloy	163
6.4	Discussion	164
6.4.1	Tensile behaviour of the modified 9 Cr-1Mo steel	164
6.4.2	Tensile behaviour of Inconel 617 alloy	169
6.5	Summary	172
CHAPTER 7	MAJOR CONCLUSIONS AND SCOPE FOR FUTURE WORK	175-181
7.1	Introduction	175
7.2	Major Conclusions	175
7.2.1	Ratcheting fatigue behaviour of modified 9Cr-1Mo steel at RT	175
7.2.2	Ratcheting fatigue behaviour of Inconel 617 alloy at RT	177
7.2.3	Ratcheting fatigue behaviour of modified 9Cr-1Mo steel and Inconel 617 alloy at elevated temperatures	178
7.2.4	Effect of pre-ratcheting on tensile properties of modified 9Cr-1Mo steel and Inconel 617 alloy at RT	179
7.3	Scope for Future Work	181
References		182-190
List of Publications		191

LIST OF FIGURES

Figure No.	Title	Page No.
1.1	Flow chart representing classification of cyclic loading with corresponding material behaviour.	2
1.2	The final deformed shape of pipe resulting from ratcheting.	4
1.3	Schematic representation of ratcheting fatigue.	5
1.4	(a) Variation of ratcheting strain with number of cycles (b) ratcheting strain rate curve exhibiting three zones for SA333C-Mn steel tested at mean stress of 80 MPa and stress amplitude of 310 MPa.	6
1.5	(a) Schematic pseudo-equilibrium Fe (with 0.1%C)-Cr phase diagram. The dashed line indicates the phase fields for the steel with 9% Cr. (b) Continuous cooling transformation diagram for 9Cr-1Mo steel.	10
1.6	TTT Diagram of Inconel 617 alloy showing temperature and time limits for formation of various phases.	23
1.7	The ratio of change in high temperature materials with steam parameters.	24
1.8	Variation of ratcheting strain with increasing cycles for different mean stresses at different constant stress amplitudes of (a) 130 MPa, (b) 140 MPa, (c) 150 MPa, (d) accumulation of total ratcheting strain upto 100 loading cycles.	26
1.9	(a) Variation of ratcheting strain with cycles at different stress amplitudes, at constant mean stress constant of 10 MPa. (b) Bar chart shows total ratcheting strain up to 100 cycles of loading (values with the bars correspond to stress amplitudes in MPa).	27
1.10	Cyclic stress-strain hysteresis loops corresponding to 10 th cycle, at different mean stresses, depicting variations in their relative positions.	28
1.11	Impact of stress rate on ratcheting fatigue of Zircaloy-2 displaying variation of ratcheting strain with cycles, at room temperature.	29
1.12	Impact of stress rate on plastic strain buildup with cycles at 400°C.	30

1.13	Evolution of ratcheting strain with cycles for 304LN stainless steel at constant stress amplitude of 420 MPa and stress rate of 50 MPa/s.	31
1.14	Ratcheting strain accumulation at RT, 300, and 400 °C under normalized mean stress (σ_m/σ_{UTS}) and stress amplitude (σ_a/σ_{UTS}) in Zircaloy -2.	32
1.15	Comparison of uniaxial ratcheting fatigue results of the prescribed <i>fcc</i> metals with different values of fault energy.	33
1.16	Comparison of uniaxial ratcheting results for the prescribed metals with different crystal structures: (a) $0.15 \pm 1.0\sigma_p 0.2$; (b) $0.15 \pm 1.1\sigma_p 0.2$.	33
1.17	Comparison of ratcheting fatigue of the SA333C-Mn steel under true and engineering stress control at a mean stress of 80 MPa and stress amplitudes of 310 and 350 MPa.	34
1.18	Comparison of yield strength and ultimate tensile strength of the un-ratcheted and ratcheted specimens of the investigated IF steel: (a) at constant stress amplitude and varying mean stresses, (b) at constant mean stress and varying stress amplitudes.	35
1.19	Variations in the width of hysteresis loops showing cyclic hardening phenomenon for the investigated IF steel.	36
1.20	Dislocation density variation under cyclic stressing conditions of $\sigma_m=30$ MPa: (a) at $\sigma_a=140$ MPa, (b) at $\sigma_a=150$ MPa.	38
1.21	(a) Occurrence of through-wall crack indicated by a sharp water jet: ratcheting experiment conducted with internal pressure of 39.2 MPa and displacement of ± 41 mm i.e. maximum load range ± 272 kN, (b) Percentage increase in diameter vs. number of cycles during ratcheting test on the elbow specimen with internal pressure of 37.9 MPa and displacement of ± 51 mm i.e. maximum load range ± 309 kN.	39
2.1	Geometry of the cylindrical tensile specimen.	44
2.2	Schematic of cylindrical fatigue specimen.	44
2.3	Schematic of asymmetric stress controlled cyclic loading, where stress ratio ($R \neq -1$), mean stress ($\sigma_m \neq 0$) and stress amplitude ($\sigma_a \neq 0$).	46
2.4	Servo-hydraulic Material Testing System (MTS).	47

2.5	(a) Machine set up for high temperature ratcheting fatigue experiments and (b) High temperature extensometer and thermocouples mounted on the sample.	48
2.6	Field emission scanning electron microscope (Model: FEI Quanta 200 F).	49
2.7	Transmission electron microscope (Model FEI Technai 20G ²).	50
3.1	Microstructure of the modified 9Cr-1Mo steel in normalized and tempered condition: (a) optical micrograph showing lath martensitic structure and (b) SEM micrograph depicting precipitates along grain boundaries.	53
3.2	TEM micrographs of modified 9Cr-1Mo steel showing: (a) second phase particles of M ₂₃ C ₆ carbides along the prior austenite grain boundaries and fine MX carbides within the laths (b) laths with high density of dislocations and (c) diffraction pattern of the matrix (<i>bcc</i>) and Cr ₂₃ C ₆ precipitate (<i>fcc</i>).	54
3.3	Engineering stress strain curve of the modified 9Cr-Mo steel in normalized and tempered condition, tested at a strain rate of 10 ⁻³ s ⁻¹ at room temperature.	55
3.4	Ratcheting behaviour of modified 9Cr-1Mo steel during asymmetric cyclic loading at room temperature:(a) decrease in loop width with cycles (b) variation of ratcheting strain with cycles during asymmetric cyclic loading and (c) rapid increase in ratcheting strain during the initial 10 cycles, shown on a magnified scale.	56
3.5	Influence of mean stress on ratcheting behaviour of modified 9Cr-1Mo steel showing: (a) change in ratcheting strain with cycles under different mean stresses and (b) ratcheting strain rate with number of cycles.	57
3.6	Influence of stress amplitude on ratcheting behaviour of modified 9Cr-1Mo steel showing: (a) change in ratcheting strain with cycles under different stress amplitudes and (b) ratcheting strain rate with number of cycles.	58
3.7	Influence of stress rate on ratcheting fatigue behaviour of modified 9Cr-1Mo steel showing: (a) change in ratcheting strain with cycles at different stress rates and (b) ratcheting strain rate with number of cycles.	59
3.8	Hysteresis loops of modified 9Cr-1Mo steel corresponding to stress cycle number 5, 50 and 500, at various mean stresses:	61

	(a) 190MPa (b) 200 MPa and (c) 210 MPa, at stress amplitude of 410 MPa and stress rate of 150 MPa/s.	
3.9	Effect of mean stress on hysteresis loop energy of modified 9Cr-1Mo steel, at different number of cycles, at constant stress amplitude of 410 MPa and stress rate of 150 MPa/s.	62
3.10	Variation of plastic strain energy with number of cycles, of modified 9Cr-1Mo steel, at different mean stresses, at constant stress amplitude of 410 MPa and stress rate of 150 MPa/s.	63
3.11	TEM micrographs of the modified 9Cr-1Mo steel in normalized and tempered condition, tested at the mean stress of 210 MPa, stress amplitude of 400 MPa, stress rate of 150 MPa/s showing: (a) easy movement of dislocations, (b) arrows show interaction of dislocations and precipitates whereas circles indicate pinning of dislocations and (c) formation of substructure by a process of dynamic recovery.	64
3.12	Hysteresis loops of modified 9Cr-1Mo steel corresponding to cycle number 5, 50 and 500 at various stress amplitudes: (a) 400 MPa (b) 410 MPa and (c) 420 MPa, at mean stress of 200 MPa and stress rate of 150 MPa/s.	65
3.13	Effect of stress amplitude on hysteresis loop energy of modified 9Cr-1Mo steel, at different number of cycles at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	66
3.14	Variation of plastic strain energy with number of cycles of modified 9Cr-1Mo steel, at different stress amplitudes at constant stress of 200 MPa and stress rate of 150 MPa/s.	67
3.15	Hysteresis loops of modified 9Cr-1Mo steel corresponding to cycle number 5, 50 and 500, at different stress rates: (a) 50 MPa/s, (b) 150 MPa/s and (c) 450 MPa/s at mean stress of 200 MPa and stress amplitude of 410 MPa.	68
3.16	Effect of stress rate on hysteresis loop energy of modified 9Cr-1Mo steel, at different number of cycles at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	69
3.17	SEM fractographs of modified 9Cr-1Mo steel fatigue sample tested, under asymmetrical cyclic loading at stress amplitude of 400 MPa , mean stress of 200 MPa and stress rate of 150 MPa/s: (a) full view of the fracture end with flat fracture surface and tapered annular region (b) magnified view of the surface from the annular region showing features like striations (c) magnified view of the flat transverse fracture surface showing dimples and	70

	(d) magnified view of the junction of the annular region showing striations in the annular region on left side and dimples on the flat surface on the right side.	
3.18	Features of modified 9Cr-1Mo steel fatigue specimen fractured under ratcheting fatigue: (a) fatigue specimen fractured from ratcheting fatigue showing necking (b) schematic presentation of the fracture end in vertical orientation showing flat surface in the central region with dimples and annular region showing striation like features and (c) isometric view of the fracture end showing flat fracture surface at the top with dimples and tapered surface of cone like frustum with striations.	71
3.19	SEM fractographs of modified 9Cr-1Mo steel fatigue sample, tested under symmetrical cyclic loading (without mean stress) at stress amplitude of 510 MPa and stress rate of 150 MPa/s showing: (a) absence of annular region and (b) magnified view of the fracture surface showing striations on the fracture surface in the region of fatigue crack propagation.	72
3.20	Bright field TEM micrographs showing stages of deformation in the modified 9Cr-1Mo steel in different loading conditions of stress amplitude, mean stress and stress rate at RT under asymmetrical cyclic loading showing : (a) forest dislocations (stress amplitude of 400 MPa , mean stress of 200 MPa, stress rate of 150 MPa/s) (b) pinning of dislocations by very fine carbide precipitates shown by circles and arrows (stress amplitude of 400 MPa , mean stress of 200 MPa, stress rate of 150 MPa/s) (c) dislocation cells (stress amplitude of 410 MPa , mean stress of 200 MPa, stress rate of 150 MPa/s and (d) recovered subgrain structure (stress amplitude of 400 MPa, mean stress of 210 MPa, stress rate of 150 MPa/s).	74
3.21	Shifting of 20 th cycle loop towards tensile direction of modified 9Cr-1Mo steel, due to increase in (a) mean stress from 190 MPa to 210 MPa (b) stress amplitude from 400 MPa to 420 MPa and (c) stress rate from 50 MPa/s to 450 MPa/s.	75
3.22	Dependence of plastic strain energy on mean stress of modified 9Cr-1Mo steel corresponding to 20 th cycle at stress amplitude of 410 MPa and stress rate of 150 MPa/s.	76
3.23	Bright field TEM micrograph of modified 9Cr-1Mo steel fatigue sample, tested at mean stress of 190 MPa, stress amplitude of 400 MPa and stress rate of 150 MPa/s, showing dislocation cell walls (incomplete recovery).	77

3.24	Bright field TEM micrograph of modified 9Cr-1Mo steel fatigue sample, interrupted at 2205 cycles, tested at stress amplitude of 410 MPa, mean stress of 200 MPa, and stress rate of 150 MPa/s, showing extended stepped dislocation (jogs).	78
3.25	STEM micrograph and EDX analysis of of modified 9Cr-1Mo steel fatigue sample, interrupted at 2205 cycles, tested at stress amplitude of 410 MPa, mean stress of 200 MPa, and stress rate of 150 MPa/s, showing: (a) region of mapping (b) matrix (c) Cr (d) Fe and (e) V.	78
3.26	Dependence of plastic strain energy on stress amplitude of modified 9Cr-1Mo steel, corresponding to 20 th cycle at mean stress of 200 MPa and stress rate of 150 MPa/s.	80
3.27	TEM micrographs of of modified 9Cr-1Mo steel fatigue sample, tested at different stress amplitudes showing: (a) elongated lath structure at stress amplitude of 400 MPa, mean stress of 200 MPa and stress rate of 150 MPa/s (b) equiaxed structure at stress amplitude of 420 MPa , mean stress of 200 MPa and stress rate of 150 MPa/s (c) matrix and precipitates at stress amplitude of 400 MPa , mean stress of 200 MPa and stress rate of 150 MPa/s and (d) diffraction pattern of the matrix and precipitate (Cr_{23}C_6).	81
3.28	Dependence of plastic strain energy on stress rate of modified 9Cr-1Mo steel, corresponding to: (a) 20 th cycle (b) 50 th , 500 th and 1000 th cycle at mean stress of 200 MPa and stress amplitude of 410 MPa.	82
3.29	Bright field TEM micrographs of modified 9Cr-1Mo steel fatigue sample, tested at different stress rates showing: (a) recovered structure at stress rate of 50 MPa/s, stress amplitude of 410 MPa and mean stress of 200 MPa (b) formation of dislocation cells along with dense forest dislocations at stress rate of 450 MPa/s, stress amplitude of 410 MPa and mean stress of 200 MPa.	83
4.1	Microstructure of the Inconel 617 alloy in solution treated (1175°C/40 min/WQ) condition: (a) optical micrograph showing single phase matrix (γ) and (b) SEM micrograph showing M_{23}C_6 carbide particles along grain boundaries.	87
4.2	Bright field TEM micrographs of the Inconel 617 alloy in solution treated condition showing: (a) M_{23}C_6 carbide particles along grain boundaries and (b) Diffraction pattern confirming precipitates of M_{23}C_6 carbide (<i>fcc</i>) with cube on cube orientation relationship with the matrix (<i>fcc</i>).	88

4.3	Engineering stress-strain curve of Inconel 617 alloy.	89
4.4	Ratcheting fatigue behaviour of Inconel 617 alloy during asymmetric cyclic loading: (a) drastic decrease in loop width after 1 st cycle (b) variation of ratcheting strain with cycles till fracture and (c) increase in ratcheting strain during the initial 50 cycles.	90
4.5	Effect of stress amplitude on ratcheting strain variation with cycles of Inconel 617 alloy.	92
4.6	Effect of stress amplitude on ratcheting fatigue of Inconel 617 alloy: (a) variation of ratcheting strain with cycles at different stress amplitudes and (b) rate of accumulation of ratcheting strain with cycles.	93
4.7	Ratcheting fatigue behaviour of Inconel 617 alloy tested at the stress amplitude close to UTS; stress amplitude of 600 MPa, mean stress of 200 MPa and stress rate of 150 MPa/s: (a) rapid increase in ratcheting strain in the beginning, followed by much slower increase up to about 12 cycles, and rapid increase till fracture (b) variation of ratcheting strain rate with cycles and (c) fractured fatigue specimen showing necking and some scratchy features on surface in the gauge section.	94
4.8	Effect of mean stress on ratcheting fatigue of Inconel 617 alloy: (a) variation of ratcheting strain with cycles under various mean stresses and (b) rate of accumulation of ratcheting strain with cycles.	95
4.9	Effect of stress rate on ratcheting fatigue of Inconel 617 alloy: (a) variation of ratcheting strain with cycles under various stress rates and (b) rate of accumulation of ratcheting strain with cycles.	97
4.10	Hysteresis loops of Inconel 617 alloy corresponding to 5, 50 and 500 stress cycles at various stress amplitudes: (a) 225 MPa (b) 250 MPa (c) 275 MPa and (d) comparison of width of the 5 th cycle loop at various stress amplitudes at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	98
4.11	Effect of stress amplitude on hysteresis loop energy of Inconel 617 alloy, at different number of cycles at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	99
4.12	Hysteresis loops of Inconel 617 alloy corresponding to 5, 50 and 500 stress cycles at various mean stresses: (a) 175 MPa, (b) 200 MPa, (c) 225 MPa and (d) comparison of width of 5 th cycle loop at various mean stresses at stress amplitude of 250 MPa	100

and stress rate of 150 MPa/s.

4.13	Effect of mean stress on hysteresis loop energy of Inconel 617 alloy, at different number of cycles at constant stress amplitude of 250 MPa and stress rate of 150 MPa/s.	101
4.14	Hysteresis loops of Inconel 617 alloy corresponding to 5, 50 and 500 stress cycles, at various stress rates: (a) 50 MPa/s, (b) 150 MPa/s, (c) 450 MPa/s. (d) comparison of width of 5 th cycle loop at various stress rates, at constant stress amplitude of 250 MPa and mean stress of 200 MPa.	102
4.15	Effect of stress rate on hysteresis loop energy of Inconel 617 alloy, at different number of cycles at constant stress amplitude of 250 MPa and mean stress of 200 MPa.	103
4.16	Fracture behaviour of Inconel 617 alloy, showing the effect of stress amplitude at: (a and b) 450MPa (c and d) 550 MPa at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	104
4.17	Fracture behaviour of Inconel 617 alloy, showing the effect of mean stress at: (a and b) 150 MPa (c and d) 250 MPa at constant stress amplitude of 500 MPa and stress rate of 150 MPa/s.	105
4.18	Fracture behaviour of Inconel 617 alloy, showing the effect of stress rate at: (a and b) 50 MPa/s (c and d) 450 MPa/s at constant mean stress of 200 MPa and stress amplitude of 500 MPa.	105
4.19	(a) Cumulative ratcheting strain vs. number of cycles (b) ratcheting strain rate and (c) hysteresis loops corresponding to 20 th cycle of modified 9Cr-1 Mo steel and Inconel 617 alloy.	107
4.20	Variation in the 20 th cycle hysteresis loops of Inconel 617 alloy, due to increase in:(a) stress amplitude from 450 to 550 MPa, (b) mean stress from 150 to 250 MPa and (c) stress rate from 50 to 450 MPa/s.	108
4.21	Variation in plastic strain energy at the 20 th cycle of Inconel 617 alloy, due to increase in:(a) stress amplitude from 450 to 550 MPa, (b) mean stress from 150 to 250 MPa and (c) stress rate from 50 to 450 MPa/s.	110
4.22	Bright field TEM micrographs of Inconel 617 alloy, showing the effect of stress amplitude at: (a and b) 450 MPa (c and d) 550 MPa, tested at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	111

4.23	Bright field TEM micrographs of Inconel 617 alloy, showing the effect of mean stress at: (a and b) 150 MPa(c and d) 250 MPa, tested at constant stress amplitude of 500 MPa and stress rate of 150 MPa/s.	113
4.24	Bright field TEM micrographs of Inconel 617 alloy, showing the effect of stress rate on dislocation substructure, tested at constant stress amplitude of 450 MPa and mean stress of 200 MPa, at: (a) 50 MPa/s (b) 450 MPa/s.	115
4.25	Fractographs of both alloys tested under ratcheting: (a and c) modified 9Cr-1Mo steel, (b and d) Inconel 617 alloy.	117
5.1	Influence of mean stress on ratcheting behaviour of modified 9Cr-1Mo steel, at 600°C showing: (a) variation of ratcheting strain with cycles under different mean stress and (b) variation of ratcheting strain rate with cycles.	121
5.2	Fracture surface of modified 9 Cr-1Mo steel ratcheted at 600°C: (a) full view of the fracture surface (b) magnified view of the annular region, below the fracture surface, showing striations like features and (c) magnified view of the central region of the fracture surface showing dimples.	122
5.3	Influence of temperature on ratcheting behaviour of modified 9Cr-1Mo steel: (a) variation of ratcheting strain with cycles and (b) variation of ratcheting strain rate with cycles at constant normalized mean stress of 0.18, normalized stress amplitude of 0.71 and stress rate of 150 MPa/s at RT and 600 °C.	124
5.4	Influence of mean stress on ratcheting behaviour of Inconel 617 alloy at 800° C showing: (a) variation of ratcheting strain with cycles under different mean stresses (b) variation of ratcheting strain rate with cycles.	126
5.5	Fracture surface of Inconel 617 alloy ratcheted at 800° C: (a) full view of the fracture surface (b) magnified view of the fatigue region showing striations (c) magnified view of striations and (d) magnified view of the tensile region showing dimples.	126
5.6	Influence of temperature on ratcheting behaviour of Inconel 617 alloy: (a) variation of ratcheting strain with cycles and (b) variation of ratcheting strain rate with cycles at constant normalized mean stress of 0.69, normalized stress amplitude of 0.12 and stress rate of 150 MPa/s at RT and 800°C.	128
5.7	(a) Variation of cumulative ratcheting strain accumulation and (b) variation of ratcheting strain rate with cycles for modified	131

	9Cr-1Mo steel and Inconel 617 alloy at $0.42 T_m$ at constant normalized stress amplitude of 0.71, normalized mean stress of 0.12 and stress rate of 150 MPa/s.	
5.8	(a) Variation of cumulative ratcheting strain accumulation and (b) variation of ratcheting strain rate with cycles for modified 9Cr-1Mo steel and Inconel 617 alloy at $0.42 T_m$ at constant normalized stress amplitude of 0.71, normalized mean stress of 0.18 and stress rate of 150 MPa/s.	133
5.9	(a) Variation of cumulative ratcheting strain accumulation and (b) variation of ratcheting strain rate with cycles for modified 9Cr-1Mo steel and Inconel 617 alloy at $0.42 T_m$ at constant normalized stress amplitude of 0.71, normalized mean stress of 0.25 and stress rate of 150 MPa/s.	134
5.10	Fracture surface of modified 9 Cr-1Mo steel ratcheted at $0.42 T_m$: (a) full view of the fracture surface (b) magnified view of the annular surface, below fracture surface, showing striation like features and (c) magnified view of central region of the fracture surface showing dimples.	135
5.11	Fracture surface of Inconel 617 alloy ratcheted at $0.42 T_m$ (a) full view of the fracture surface (b) magnified view of the fatigue region showing striations and (c) magnified view of the tensile region showing dimples.	135
5.12	Bright field TEM micrograph of the modified 9Cr-1Mo steel specimen tested at 600°C showing: (a) dislocation pile up at boundaries (b) dislocation cells (yellow arrows) in the specimen tested at mean stress of 45 MPa, stress amplitude of 270 MPa and stress rate of 150 MPa/s (c) complete recovery (yellow arrow) of specimen tested at mean stress of 80 MPa, stress amplitude of 235 MPa and stress rate of 150 MPa/s and (d) beginning of recrystallization (yellow arrows) and re-precipitation of the carbides (red arrow) occurs within the recovered or recrystallized grains of the specimen tested at mean stress of 95 MPa, stress amplitude of 270 MPa and stress rate of 150 MPa/s.	137
5.13	Schematic tensile stress strain plot showing plastic strain at both the test temperatures.	138
5.14	Bright field (BF) TEM micrograph of Inconel 617 alloy, tested at 800°C under asymmetrical loading with mean stress, showing: (a) formation of carbides (b) interaction of dislocations with precipitates (c) magnified view of the second phase particle and	139

	(d) SAD pattern confirming gamma matrix and $M_{23}C_6$ precipitate.	
5.15	Influence of mean stress on ratcheting at $0.42 T_m$ for Inconel 617 alloy showing: (a) variation of ratcheting strain with cycles under different mean stress and (b) variation of ratcheting strain rate with cycles.	141
5.16	TEM micrographs of modified 9Cr-1Mo steel ratcheted at $0.42 T_m$ (a) grains clear of dislocations (b) curved boundary (green arrow) (c) dislocations pile-up at boundaries (red arrow) and (d) $M_{23}C_6$ precipitates.	141
5.17	TEM micrographs of Inconel 617 alloy ratcheted at $0.42 T_m$ (a) intersections of slip bands and (b) tangles of dislocations.	142
6.1	Hysteresis loops of decreasing width resulting from ratcheting of modified 9Cr-1Mo steel.	147
6.2	Ratcheting behaviour of modified 9Cr-1Mo steel with different variables: (a) mean stress, (b) stress amplitude and (c) stress rate.	148
6.3	Variation of 0.2% offset yield strength and ultimate tensile strength of modified 9Cr-1Mo steel due to ratcheting variables: (a) mean stress, (b) stress amplitude and (c) stress rate.	151
6.4	Fractographs of the un-ratcheted tensile tested specimen of modified 9Cr-1Mo steel.	152
6.5	Fracture behaviour of modified 9Cr-1Mo steel pre-ratcheted at mean stress of 190 MPa; stress amplitude of 410 MPa; and stress rate of 150 MPa/s and tensile tested: (a) at 200X, (b) enlarged view of the central region showing dimples and (c) enlarged view of the peripheral region showing striations like marks.	153
6.6	Hysteresis loops resulting from ratcheting of Inconel 617 alloy.	155
6.7	Ratcheting fatigue behaviour of Inconel 617 alloy with various parameters: (a and b) mean stress (c and d) stress amplitude and (e and f) stress rate; at the maximum stress close to the yield strength and ultimate tensile strength.	156
6.8	Variation of strength parameters of the specimens, pre-ratcheted at different mean stresses, at the maximum stress near: (a) yield strength and (b) ultimate tensile strength.	159
6.9	Variation of strength parameters of the specimens pre-ratcheted at different stress amplitudes, at the maximum stress near: (a) yield strength and (b) ultimate tensile strength.	161

6.10	Variation of strength parameters of the specimens pre-ratcheted at different stress rates, at the maximum stress near: (a) yield strength and (b) ultimate tensile strength.	163
6.11	Fracture behaviour of Inconel 617 alloy: (a and b) un-ratcheted specimen and (c and d) ratcheted specimen at maximum stress near yield strength and (e and f) ratcheted specimen at maximum stress near ultimate tensile strength.	163
6.12	Effect of different variables on hysteresis loops of modified 9Cr-1Mo steel: (a) mean stress (b) stress amplitude and (c) stress rate	164
6.13	Yield strength vs. hysteresis loop energy at (a) different mean stresses and (b) different stress amplitudes.	167
6.14	(a and b): TEM Bright field micrographs for un-ratcheted specimen (c) Bright field micrograph for mean stress of 210 MPa, stress amplitude of 410 MPa, stress rate of 150 MPa/s indicating pinning of boundaries by precipitate with an inset showing dark field (d) Diffraction pattern confirming BCC matrix and FCC precipitate (Cr_{23}C_6) for mean stress of 210 MPa, stress amplitude of 410 MPa, stress rate of 150 MPa/s (e) Bright field micrograph for mean stress of 210 MPa, stress amplitude of 410 MPa, stress rate of 150 MPa/s showing heavy dislocation pile up (f) Bright field micrographs for stress amplitude of 420 MPa, mean stress of 200 MPa, stress rate of 150 MPa/s depicting interaction of dislocation with solute atmosphere (g and h) Bright field micrographs for stress rate of 450 MPa/s, mean stress of 200 MPa, stress amplitude of 410 MPa showing shearing of the precipitate.	169
6.15	Effect of different variables on hysteresis loops of Inconel 617 alloy at: (a) different mean stresses (b) different stress amplitudes and (c) different stress rates.	170
6.16	TEM Bright field micrographs for un-ratcheted specimen showing: (a) slip bands (b) dislocation sub-structure.	171
6.17	TEM Bright field micrographs of the specimen ratcheted at the maximum stress near the yield strength at stress amplitude of 275 MPa and at constant mean stress of 200 MPa and stress rate of 150 MPa/s showing: (a) twinning (b) corresponding diffraction pattern showing twin plane (c) dislocation sub-structure.	172

LIST OF TABLES

Table No.	Title	Page No.
2.1	Chemical composition of the modified 9Cr-1Mo steel (weight %).	42
2.2	Chemical composition of the Inconel 617 alloy (weight %).	43
3.1	Strength and ductility parameters of the normalized and tempered modified 9Cr-1Mo steel, tested at strain rate of 10^{-3} s^{-1} , at RT.	55
3.2	Variation of fatigue life of modified 9Cr-1Mo steel, under asymmetric cyclic loading at various mean stresses, tested at stress amplitude of 410 MPa and stress rate of 150 MPa/s.	57
3.3	Variation of fatigue life of modified 9Cr-1Mo steel, under asymmetric cyclic loading at various stress amplitudes, tested at mean stress of 200 MPa and stress rate of 150 MPa/s.	58
3.4	Variation of fatigue life of modified 9Cr-1Mo steel, under asymmetric cyclic loading at various stress rates, tested at mean stress of 200 MPa and stress amplitude of 410 MPa.	59
3.5	Variation of plastic strain energy of modified 9Cr-1Mo steel, with mean stress and number of cycles.	63
4.1	Strength and ductility parameters of the Inconel 617 alloy tested, at the strain rate of 10^{-3} s^{-1} , at RT.	89
4.2	Test matrix of ratcheting fatigue tests of Inconel 617 alloy at varying stress amplitude, at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	91
4.3	Variation in fatigue life of Inconel 617 alloy under ratcheting fatigue, at varying stress amplitude, at constant mean stress of 200 MPa and stress rate of 150 MPa/s.	93
4.4	Variation in fatigue life of Inconel 617 alloy under ratcheting fatigue, at varying mean stress and at constant stress amplitude of 500 MPa and stress rate of 150 MPa/s.	95

4.5	Variation in fatigue life of Inconel 617 alloy under ratcheting fatigue at varying stress rate, at constant mean stress of 200 MPa and stress amplitude of 500 MPa.	96
4.6	Ratcheting fatigue test matrix of the alloys, at RT at constant normalized stress amplitude of 0.58, normalized mean stress of 0.29 and stress rate of 150 MPa/s.	106
5.1	Tensile properties of the modified 9Cr-1Mo steel tested at the strain rate of 10^{-3} s^{-1} , at RT and 600°C .	120
5.2	Dependence of cyclic life of modified 9Cr-1Mo, under asymmetric loading steel at varying mean stress, at constant stress amplitude of 270 MPa and stress rate of 150 MPa/s at 600°C .	121
5.3	Ratcheting fatigue test matrix of modified 9Cr-1Mo steel at RT and 600°C , at constant normalized mean stress of 0.18, normalized stress amplitude of 0.71 and stress rate of 150 MPa/s.	123
5.4	Tensile properties of the Inconel 617 alloy at the strain rate of 10^{-3} s^{-1} , at RT and 800°C .	124
5.5	Dependence of cyclic life of Inconel 617 alloy, under asymmetric loading at varying mean stress, tested at constant stress amplitude of 255 MPa and stress rate of 150 MPa/s at 800°C .	125
5.6	Ratcheting fatigue test matrix of Inconel 617 alloy at RT and 800°C , at constant normalized mean stress of 0.69, normalized stress amplitude of 0.12 and stress rate of 150 MPa/s.	127
5.7	Tensile properties of the alloys tested at strain rate of 10^{-3} s^{-1} , at $0.42 T_m$.	130
5.8	Ratcheting fatigue test matrix of the alloys, at $0.42 T_m$ at constant normalized stress amplitude of 0.71, normalized mean stress of 0.12 and stress rate of 150 MPa/s.	131
5.9	Ratcheting fatigue test matrix of the alloys, at $0.42 T_m$ at constant normalized stress amplitude of 0.71, normalized mean stress of 0.18 and stress rate of 150 MPa/s.	132
5.10	Ratcheting fatigue test matrix of the alloys, at $0.42 T_m$ at constant normalized stress amplitude of 0.71, normalized mean stress of 0.25 and stress rate of 150 MPa/s.	133

6.1	Tensile data of the modified 9Cr-1Mo steel at room temperature at 10^{-3} s^{-1} .	146
6.2	Test matrix for ratcheting fatigue tests for 200 cycles for modified 9Cr-1Mo steel at RT.	147
6.3	Tensile data of modified 9Cr-1Mo steel pre-ratcheted at various mean stresses.	149
6.4	Tensile data of modified 9Cr-1Mo steel pre-ratcheted at various stress amplitudes.	150
6.5	Tensile data of modified 9Cr-1Mo steel pre-ratcheted at various stress rates.	150
6.6	Tensile properties of the Inconel 617 alloy tested at strain rate of 10^{-3} s^{-1} , at RT.	154
6.7	Test matrix for ratcheting fatigue tests up to 200 cycles for Inconel 617 alloy at RT, at maximum stress near the yield strength (S_{YS}).	155
6.8	Test matrix for ratcheting fatigue tests up to 200 cycles for Inconel 617 alloy at RT, maximum stress near the ultimate tensile strength (S_{UTS}).	155
6.9	Tensile data of the Inconel 617 alloy pre-ratcheted at different mean stresses, at maximum stress near the yield strength (S_{YS}).	158
6.10	Tensile data of the Inconel 617 alloy pre-ratcheted at different mean stresses, at maximum stress near the ultimate tensile strength (S_{UTS}).	158
6.11	Tensile data of the Inconel 617 alloy pre-ratcheted at different stress amplitudes, at maximum stress near the yield strength (S_{YS}).	160
6.12	Tensile data of the Inconel 617 alloy pre-ratcheted at different stress amplitudes, at maximum stress near the ultimate tensile strength (S_{UTS}).	160
6.13	Tensile data of the Inconel 617 alloy pre-ratcheted at different stress rates, at maximum stress near the yield strength (S_{YS}).	162

6.14	Tensile data of the Inconel 617 alloy pre-ratcheted at different stress rates, at maximum stress taken near the ultimate tensile strength (S_{UTS}).	162
-------------	--	------------

LIST OF SYMBOLS

LCF	Low cycle fatigue
HCF	High cycle fatigue
PAGb	Prior austenite grain boundary
BCC	Body centered cubic
FCC	Face centered cubic
ϵ_r	Ratcheting strain
ϵ_{max}	Maximum strain at a particular cycle
ϵ_{min}	Minimum strain at the cycle
σ_a	Stress amplitude
σ_m	Mean stress
$\dot{\sigma}$	Stress rate
σ_{max}	Maximum stress
σ_{min}	Minimum stress
N_f	Number of cycles to failure
σ_{na}	Normalized stress amplitude
σ_{nm}	Normalized mean stress
S_{YS}	Yield strength
S_{UTS}	Ultimate tensile strength
e_u	Uniform elongation
e_f	Total elongation
RA	Reduction in area
n	Strain hardening exponent
K	Strength coefficient
R	Stress ratio

TEM	Transmission electron microscope
SEM	Scanning electron microscope
STEM	Scanning transmission electron microscope
EDX	Energy dispersive X-Ray spectroscopy
BF	Bright field
DF	Dark field
SAD	Selected area diffraction

PREFACE

The advanced power generating industries use high operating steam temperatures and pressures, to achieve higher efficiency. This led to development of alloys with superior properties at elevated temperatures. The two alloys under investigation are modified 9Cr-1Mo steel and Inconel 617 alloy. From the application point of view, the two alloys are used as piping and tubing materials in various components such as steam generator, super heater, re heater and heat exchanger etc. of power plants. Modified 9Cr-1Mo steel (grade 91) with strengthening elements such as Mo, V and Nb added to conventional 9Cr-1Mo steel possesses excellent mechanical properties, microstructural stability at elevated temperatures and resistance to corrosion in comparison to low Cr-Mo steels, conventional 9Cr-1Mo and austenitic stainless steels. Addition of Cr improves the corrosion resistance and mechanical properties. Mo is a solid solution strengthener and is considered as a retardant for dislocation recovery/recrystallization. In this alloy, strength in normalized and tempered condition is derived from carbides like NbC, VC and $M_{23}C_6$ on sub-boundaries and from tempered martensitic laths with high dislocation densities. The other alloy under investigation is Inconel 617 alloy, which is a nickel based superalloy containing Cr, Co, Mo, Al and Ti as alloying elements. It is widely used in, high temperature applications because of its superior creep resistance and improved stability of microstructure for long exposures at elevated temperatures. A protective layer of Cr and Al oxides, forms on the surface of the alloy at elevated temperature, enhances its oxidation resistance. This tungsten free alloy is lighter and cost competitive as compared to other nickel based alloys with tungsten. It is primarily strengthened by, precipitation of fine homogeneously dispersed γ' phase in γ matrix and from precipitation of M_6C and $M_{23}C_6$ carbides, both at grain boundaries and in the grains.

Failure occurring under cyclic loading is termed as fatigue. The loading condition may change from symmetric to asymmetric. In low cycle fatigue, there is symmetrical loading ($R=-1$); therefore, plastic strain does not accumulate, whereas in asymmetrical loading hysteresis loops do not close, and plastic strain increases due to imposition of positive mean stress and this process is termed as ratcheting or cyclic creep. Due to progressive increase in tensile permanent deformation, cyclic life is drastically reduced, in respect of the low cycle fatigue. During service, components such as pipes and tubes in various industries and power plants undergo ratcheting due to fluctuation in internal pressure, temperature and seismic events; therefore, during the last three decades ratcheting fatigue has gained much importance. Various investigations have been conducted on different structural materials (e.g. different grades of steel, alloys of aluminium, copper, zirconium, magnesium, polymers etc.) in the area of ratcheting fatigue. However, the area of ratcheting under various parameters along with microstructural correlation is still unexplored, for the two alloys under study. The present investigation, aims to investigate the ratcheting fatigue behaviour of modified 9Cr-1Mo steel and Inconel 617 alloy, under various parameters (stress amplitude, mean stress, stress rate and temperature) along with deformation and fractography in detail. The thesis is divided into seven chapters.

Chapter 1- presents introduction of ratcheting fatigue and literature related to it, for various structural materials under different areas of experimentation, microstructural characterization and modelling. The alloys investigated in this study are modified 9Cr-1Mo steel and Inconel 617 alloy. There is brief introduction of both the alloys regarding design, development, physical metallurgy and applications. The need and importance of the present investigation is emphasized along with objectives of the study.

Chapter 2- presents details of materials and experiments carried out in the present investigation. Modified 9Cr-1Mo steel was obtained in normalized and tempered

condition, in the form of 25 mm plate thickness whereas Inconel 617 alloy was procured as forged rod of 14 mm diameter and was solution annealed at 1175°C for 40 minutes and quenched in water. For finalizing the matrix for ratcheting fatigue experiments, tensile tests were conducted for both the alloys at a strain rate of 10^{-3} s^{-1} and at different temperatures. Ratcheting fatigue experiments were performed under asymmetrical loading, in stress controlled mode, for modified 9Cr-1Mo steel and Inconel 617 alloy under various parameters such as stress amplitude, mean stress, stress rate and temperature.

Fracture surfaces of the tensile and fatigue tested specimens were examined by scanning electron microscope. Deformation behaviour was analyzed using transmission electron microscope.

Chapter 3- deals with ratcheting fatigue behaviour of modified 9Cr-1Mo steel at room temperature. The effect of mean stress, stress amplitude and stress rate on ratcheting behaviour of modified 9Cr-1Mo steel was analyzed. It was observed that with increase in mean stress and stress amplitude, the accumulation of ratcheting strain increases whereas fatigue life decreases. Contrarily, with rise in stress rate, ratcheting strain decreases and there is enhancement in fatigue life, for the alloy investigated. On examining the fracture surface, a unique type of fracture was observed in case of modified 9Cr-1Mo steel with two distinct regions: the central region of the fracture surface showing dimples and the circumferential region depicting striations like features. Microstructural characterization on deformation under ratcheting showed that, in case of Modified 9Cr-1Mo steel the lath martensitic microstructure transformed into equiaxed subgrain structure (recovery).

Chapter 4- discusses the ratcheting fatigue behaviour of Inconel 617 alloy at room temperature. The effect of mean stress, stress amplitude and stress rate on ratcheting

behaviour of Inconel 617 alloy was analyzed. Ratcheting strain increases with increase in mean stress and stress amplitude and fatigue life reduces whereas inverse behaviour was observed with rise in stress rate. Inconel 617 alloy exhibited typical fatigue fracture with striations. Microstructural characterization following deformation under ratcheting, exhibited slip bands at regular intervals.

Ratcheting fatigue behaviour of both the alloys at room temperature was compared with the help of normalized mean stress and stress amplitude at a constant stress rate of 150 MPa/s. It was observed the accumulation of ratcheting is very high for Inconel 617 alloy in comparison to modified 9Cr-1Mo steel. In spite, of such high accumulation of plastic strain in Inconel 617 alloy, it still exhibited higher fatigue life. The reason for observed behaviour is higher value of uniform elongation and degree of work hardening in Inconel 617 alloy. Thus, uniform elongation can be considered as an important tensile parameter for selection of material for piping and tubing components, experiencing ratcheting fatigue.

Chapter 5- presents the ratcheting fatigue behaviour of modified 9Cr-1Mo steel and Inconel 617 alloy at their respective service temperature, under the influence of mean stress. The service temperature for modified 9Cr-1Mo steel is 600° C whereas for Inconel 617 alloy it ranges between 750°C- 850°C; therefore it is taken as 800° C, in the present investigation. With increase in mean stress the ratcheting strain increases, and there is reduction in fatigue life, for the two alloys under study at their respective service temperatures. Apart from this, the ratcheting behaviour of the two alloys at ambient temperature has been compared with their respective service temperatures. Hence, for the purpose of comparison the two parameters i.e. the stress amplitude and mean stress were normalized, with respect to tensile strength of the alloys, at that particular temperature, and the third parameter of stress rate was kept constant at 150 MPa/s. The comparison

showed that for both the alloys, with increase in temperature, ratcheting strain decreases and there is improvement in the cyclic life of the alloy. The enhancement in fatigue life of the alloys at their respective service temperature may be attributed to modulus of elasticity and recovery processes. The fracture surfaces showed similar type of features as observed at room temperature for the two alloys under investigation. On examining the microstructures of the samples, deformed under ratcheting at elevated temperature, recovery along with recrystallization was observed for modified 9Cr-1Mo steel whereas there was formation of precipitates ($M_{23}C_6$) in Inconel 617 alloy.

The next part of the chapter deals with, ratcheting behaviour of the alloys at identical homologous temperature. The best way to compare the mechanical properties of different materials, at elevated temperatures is in terms of the ratio of the test temperature to the melting point, expressed in degrees Kelvin. This ratio is often referred to, as homologous temperature. This ratio in the present study, figures out to be $0.42 T_m$. Ratcheting fatigue tests were conducted at $0.42 T_m$ with normalized mean stress, stress amplitude and at a constant stress rate of 150 MPa/s to study the behaviour of both the alloys. While comparing the behaviour of the two alloys it was observed that ratcheting strain accumulation was tremendously high for Inconel 617 alloy as compared to modified 9Cr-1Mo steel. The ratcheting curve shows steps at various intervals in case of Inconel 617 alloy whereas the curve is highly stable for modified 9Cr-1Mo steel. The abrupt increase in plastic strain accumulation, in Inconel 617 alloy may be attributed to unpinning effect of dislocations, pinned due to dynamic strain aging. Modified 9Cr-1Mo steel exhibits striations like features on smooth circumferential region and dimples in the central region of the fracture surface whereas Inconel 617 alloy depicts purely fatigue signature (striations). The deformation behaviour of modified 9Cr-1Mo steel at $0.42 T_m$ exhibits dislocation pile-ups, at boundaries along with precipitates which may provide

barriers to the mobility of dislocations, on the other hand tangles of dislocations along with cross slipping was observed for Inconel 617 alloy.

Chapter 6- deals with the influence of ratcheting on tensile properties of modified 9Cr-1Mo steel and Inconel 617 alloy under the impact of mean stress, stress amplitude and stress rate at ambient temperature. The strength parameters increased while ductility decreased for ratcheted specimens as compared to the un-ratcheted specimen. With increase in mean stress and stress amplitude, the strength parameters increased while the ductility decreased for the two alloys under investigation. This can be very well explained with the cyclic hardening behaviour of the alloys under these two parameters.

Inversely, with increase in stress rate the strength parameters decreased while ductility increased and this behaviour is mainly attributed to the cyclic softening behaviour of the alloys. Inconel 617 alloy showed tremendous increase in yield strength of about 186% in comparison to modified 9Cr-1Mo steel. While examining the fracture surface, modified 9Cr-1Mo steel exhibited rosette fracture for un-ratcheted specimen, and for ratcheted specimen distinct regions have been observed, central region showing dimples and the circumferential region depicting striations like feature. Inconel 617 alloy showed purely ductile fracture with dimples on fracture surface, for ratcheted as well as un- ratcheted specimens. Microstructural characterization to observe the basic difference in deformation due to pre-ratcheting and to see the effect of the parameters was performed by transmission electron microscopy.

Chapter 7- summarizes the major conclusions of the present investigation and scope for future work.